

# ASTM C1609 Accessory Package

## ASTM C1609 Fixture



Designed according to ASTM C1609, ASTM C1812, and ASTM C78

Includes the averaging flex fixture with ASTM C1812 compliant roller supports, cage, and two displacement transducers with holders at mid-span mounted on either side of the beam.

Net deflection is the average of two displacement sensors placed on either side of the specimen. This configuration ensures accurate measurement of mid-span deflection and minimizes errors due to concrete specimen twisting or seating in the supports.

For further information on ASTM C1609 testing, click [here](#).

Item number	FT-100T-C1609
Maximum Capacity	100 kN (22,480lbf)
Upper Bar Length	240 mm with adjustable adapter
Roller Diameter	500 mm
Support Options	30 mm
Temperature Range	0 - 180 C
Material/Finish	Steel
Connection Size	31.8 mm or 40 mm Female eye end

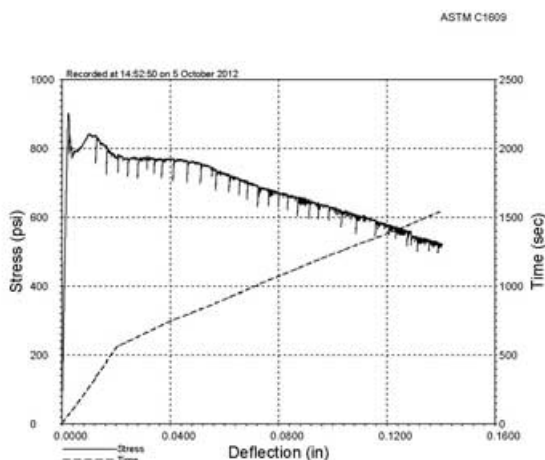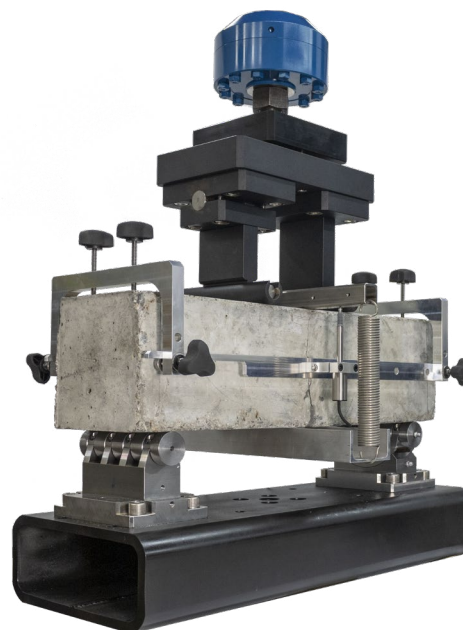

Specimen Identifier:	2
Test#:	21
Operator:	RTG
Support Span (in):	18
Nose Span (in):	6
L/900 Rate 1 (in/min):	0.002
L/150 Rate 2 (in/min):	0.007
Test Date:	5 October 2012
Start Time:	14:52:50
End Time:	15:18:35
Geometry:	Beam 3rd
Width:	6.2500 in
Depth:	6.0000 in
Span Length:	18.0000 in
Axial Strain Gauge Length:	1.0000 in
Transverse Strain Gauge Length:	1.0000 in
Area:	12.5000 sq in
<b>Analysis Results</b>	
ASTM C1609/C1609M	
Load at 1st Peak	11269 lb
Deflection at 1st Peak	0.0025 in
Strength at 1st Peak	902 psi
Load at Peak	11269 lb
Deflection at Peak	0.0025 in
Strength at Peak	902 psi
Residual Load at L/600	9058 lb
Residual Strength at L/600	773 psi
Ratio at L/600	85.7 %
Residual Load at L/150	7243 lb
Residual Strength at L/150	579 psi
Ratio at L/150	64.3 %
Residual Load at L/300	9085 lb
Residual Strength at L/300	727 psi
Ratio at L/300	80.6 %
Residual Load at L/400	8554 lb
Residual Strength at L/400	764 psi
Ratio at L/400	84.8 %
Toughness at L/600	250 lbfm
Toughness at L/150	1061 lbfm
Equivalent Strength (ft3)	707 psi
Strength Ratio (Re3)	78.5 %